



ELSEVIER

Available online at www.sciencedirect.com

SciVerse ScienceDirect

<http://www.elsevier.com/locate/biombioe>

Investigation of combined catalyst and oxygen carrier systems for the partial oxidation of naphthalene as model tar from biomass gasification

M. Ma^{a,*}, M. Müller^a, J. Richter^b, R. Kriegel^b, D. Böhning^c,
M. Beckmann^c, J. Glüsing^d, N. Ruhe^d

^aForschungszentrum Jülich GmbH, Institute of Energy and Climate Research (IEK-2), Leo-Brandt-Strasse, D-52425 Jülich, Germany

^bFraunhofer Institute for Ceramic Technologies and Systems IKTS, Hermsdorf, Germany

^cTechnische Universität Dresden, Institute for Energy Technology, Dresden, Germany

^dHAASE Energietechnik GmbH, Neumünster, Germany

ARTICLE INFO

Article history:

Received 15 June 2012

Received in revised form

26 October 2012

Accepted 25 November 2012

Available online 20 December 2012

Keywords:

Biomass gasification

Catalytic conversion

Partial oxidation

Sour gas sorbent

Tar removal

ABSTRACT

In this paper, catalytic partial oxidation is applied as a thermo-chemical method to remove tar (here: naphthalene as a model component for tar) from Syngas and convert it into fuel gas by using a combined catalyst and oxygen carrier system. In this method, the amount of oxygen needed for the partial oxidation of tar will be supplied by an oxygen carrier, which will also serve as a carrier of the catalyst. Based on the results of laboratory tests, the perovskite material CSFM ($\text{Ca}_{0.5}\text{Sr}_{0.5}\text{Fe}_{0.5}\text{Mn}_{0.5}\text{O}_{3-\delta}$) and ilmenite exhibited promising properties as oxygen carriers. They can supply a sufficient amount of oxygen for the oxidation of tar and show excellent redox properties for the regeneration. As a potential catalyst material, NiO showed high catalytic activity. During testing, the combined system of these two materials showed high ability for the removal of naphthalene, which was used as a model component for tar. In order to prevent the catalyst (NiO) from being poisoned by H_2S , H_2S sorbent was used. In combination with the combined catalyst and oxygen carrier system, the use of H_2S sorbent further enhanced the performance of the catalyst. In conclusion, the suitable oxygen carrier materials, catalyst and sour gas sorbent could be identified, which in combination enable the proposed tar removal process.

© 2012 Elsevier Ltd. All rights reserved.

1. Introduction

The gasification technology provides a method for the energetic use of biomass. The application of gasification technology to generate electricity and heat makes it possible to realize small, decentralized plants with regional energy-

supply structure and a higher efficiency. One disadvantage of gasification is the formation of undesired high boiling hydrocarbons and tars [1–3]. This limits significantly the use of gas in a CHP unit (combined heat and power unit) and delays the establishment of this technology in the market. The current state of development for tar removal is still not

* Corresponding author.

E-mail address: m.ma@fz-juelich.de (M. Ma).

0961-9534/\$ – see front matter © 2012 Elsevier Ltd. All rights reserved.

<http://dx.doi.org/10.1016/j.biombioe.2012.11.014>

sufficient to guarantee a safe and economical operation. For instance, by using the produced fuel gas for gas engines, very high requirements are made on the quality of the fuel gas. These requirements are at present either not reached, or only will be reached with a very high expense on apparatus and operational techniques. As a physical process, gas scrubbing can remove disturbing components from the gas [4]. However, the disadvantage of this method is the yielding of PAH-containing sludge and phenol-containing wastewater. These must be further processed by appropriate operation, which needs either a large amount of technical effort or high costs.

One more effective method with little sludge and wastewater for tar removal and conversion is the catalytic partial oxidation method, which is a catalytically active thermo-chemical process. Partial oxidation means that the reaction will take place with a sub-stoichiometrical amount of oxygen, so that the CH- and CHO-compounds (tars) will be partially oxidized to CO and H₂ instead of completely oxidizing to CO₂ and H₂O. An oxidative catalytic tar removal can be achieved by using a catalyst and injecting air to the fuel gas [5,6]. Nevertheless, the use of air as oxidant brings also some drawbacks, such as dilution of the fuel gas and total oxidation of fuel gas components.

In this paper, a combined system of an oxygen carrier material (OCM: abbreviation for Oxygen Carrier Material) and a catalyst for the partial oxidation of naphthalene (as a model component for tar) will be introduced. OCMs are able to incorporate oxygen ions into the crystal lattice. The oxygen stoichiometry of the ceramic material depends significantly on oxygen partial pressure and temperature. Therefore, such compounds can be used in a process called CAR (Ceramic Auto-thermal Recovery) based on a cyclic variation of the oxygen partial pressure [7]. Oxides based on the perovskite structure type show very high oxygen storage capacity [8]. The OCM releases the necessary oxygen and the partial oxidation of the high boiling hydrocarbons (tars) can be activated by the catalyst. Meanwhile, the OCM also serves as a carrier for the catalyst. There are so far hardly any systems known for this specific application in the literature. In accordance with the CLC process (chemical looping combustion) [9,10], a gas processing apparatus was developed, which comprises of two reactors. The reactors operate alternately with tar-containing Syngas and with air. While the operation with tar-containing Syngas removes tar and consumes oxygen in the combined catalyst and OCM system (catalytic partial oxidation), the operation with air regenerates the combined catalyst and OCM system so that it can be used again for the next tar removal process. During the tar removal, the oxygen will be released from the OCM. When reaching or just about to reaching the oxygen depletion in the OCM, the gas media in the two reactors will be switched. The oxygen-depleted carrier will now be regenerated by the oxygen in air; while simultaneously the regenerated OCM will operate with the tar-containing Syngas. In this way, a continuous tar removing process can be achieved. A model has already been developed, which describes the condensation of tars, the oxygen release during heat up and the reaction between tars and oxygen [11]. By this model, the demands on the capacity and temperature dependant release behaviour of the OCM can be determined.

2. Experimental

2.1. Materials selection

As OCM, CSFM (Ca_{0.5}Sr_{0.5}Fe_{0.5}Mn_{0.5}O_{3-δ}) and ilmenite were selected. CSFM is a perovskite material known for its reversible oxygen stoichiometry and phase stability [12,13]. It has been synthesized by solid state reaction of the appropriate amounts of the oxides. The oxygen for the partial oxidation of naphthalene will be released from the perovskite lattice of this material. Ilmenite (Rio Tinto Group, Fer et Titane, Sorel-Tracy/Québec, Canada) contains a large proportion of Fe_xO_y (Table 1), which serves as reversible OCM in the CLC process [9,10]. Compared to CSFM, ilmenite is a natural and more cost effective material. As the catalyst material, NiO was selected. It is a common catalyst material, widely used in the field of SOFC (solid oxide fuel cell) as the catalytic ingredient of the anode materials and catalyses the oxidation of the fuel [14,15]. The 2-aromatic ring molecule naphthalene (C₁₀H₈) was used as a tar model compound for the following reasons: first of all, it is the most difficult component in tar to be decomposed by catalytic reforming. Besides, the major fraction of the two ringed aromatics in tar is in fact naphthalene [16]. Moreover, naphthalene is often used as tar model compound in the literature [16–21].

In addition to the organic impurities such as tars, the inorganic tracer H₂S will also be released during biomass gasification, which would initiate and accelerate the deactivation of catalysts [22]. In order to prevent the catalyst from being deactivated by H₂S, CuO was used as a sorbent in some experiments to reduce the trace gas [23,24]. The regeneration of Cu can be performed with air advantageously together with the OCM.

2.2. Preparation of the combined catalyst and OCM systems

For preparation of the combined catalyst and OCM system, the OCMs were first shaped into mini honeycomb structure and then coated with catalyst on the surface. By use of an extrusion tool and a cutting device, the OCMs were first extruded into mini honeycomb structure and then cut into small pieces. The extruded structure has nine flow-through channels, as can be seen in Fig. 1.

Table 1 – Chemical composition of the ilmenite.

Composition	Mass [g kg ⁻¹]
Fe	367
Ti	149
Al	30.2
Ca	12.2
Cr	0.91
Mg	29.7
Mn	1.1
Na	5
Ni	0.61
Si	51.6
Zr	0.81
O	336.9



Fig. 1 – OCM in the shape of mini honeycomb.

In the next step, the formed OCMs were sintered at 1350 °C (2 h dwell times) for CSFM and at 1300 °C (2 h dwell times) for ilmenite, respectively. Both materials were then coated with the catalyst. In the coating process, the honeycombs were immersed into a catalyst slurry suspension. At the same time, a slight low pressure was applied to deaerate the remained air from the channels of the mini honeycombs. Afterwards, the honeycombs were removed from the catalyst slurry by a sieve and placed individually on an absorbent pad. After drying in air for 48 h, the honeycombs were sintered again at 1000 °C for 1 h.

In this way, 3 batches of CSFM and 1 batch of ilmenite coated with different weight portions of NiO were produced as combined catalyst and OCM systems for naphthalene removal (Table 2). Fig. 2 shows the scanning electron microscope (SEM) analysis of the catalyst-coated OCM. It can be seen that the material has a large contact surface with the catalyst. The fine grained catalyst penetrated deeply into the pores of the honeycomb structured OCM and is equally distributed. The layer thickness of the catalyst is in the micrometre range.

2.3. Testing of OCMs

The redox properties of the OCMs were determined by thermogravimetric analyses. By using this method, the mass change of the OCM can be continuously measured as a function of temperature and/or time. In this study, a magnetic suspension balance from Rubotherm Präzisionsmesstechnik

GmbH is applied for the mass measurement, which also allows measurements under harsh conditions [25].

The properties of the OCMs were examined in a long-term four-cycle experiment. In the first cycle the pre-oxidation phase occurs. In this phase, the OCM was fully oxidized during heating up to 900 °C with 25 cm³ min⁻¹ air flow. After that, the material was cooled down to 100 °C in the same gas atmosphere. In the next cycle, the gas flow was changed to Ar/H₂ with a flow rate of 25 cm³ min⁻¹. The OCM was then heated up to 800 °C in this reducing atmosphere. Because of the low O₂ partial pressure, the oxygen stored in the OCM would then be released in this reduction phase. Afterwards, a re-oxidation phase (the 3rd cycle) with air flow and a further reduction phase (the 4th cycle) with Ar/H₂ gas flow were repeated to test the reversibility of this material. Through this cyclic long-term experiment with gas exchange of air and Ar/H₂, the oxygen storage capacity, reversibility and stability of the OCM can be identified. The materials were characterised by XRD before and after the experiments.

2.4. Testing of the catalyst activity and naphthalene removability of the combined catalyst and OCM systems

The ability for naphthalene removal of the combined catalyst and OCM systems as well as the catalyst activity was examined by using molecular beam mass spectrometry (MBMS). The MBMS can provide effective in situ analysis of high-temperature condensable and non- condensable gases [26,27]. The experimental setup is shown in Fig. 3.

The experiments were conducted in a high density alumina tube in order to avoid side reactions. The mini honeycombs to be tested were placed in the alumina tube as a fill and the tube was then placed in the 5-zone furnace. The carrier gas (helium with 40 mmol mol⁻¹ hydrogen) was first loaded with a naphthalene concentration of 2 ± 0.02 g m⁻³ by flowing over a fixed naphthalene source. The exact amount of naphthalene vaporized during an experiment was determined by weighing the source before and after the experiment. The naphthalene loaded carrier gas was then led via a flange into the reaction tube and flows constantly (3 dm³ min⁻¹) through the mini honeycomb fill. To make a direct analysis of the remained naphthalene concentration in the carrier gas after reacting with the mini honeycomb fill, the 5-zone furnace was connected to an MBMS. During the experiment, the furnace temperature rose from 300 °C with a heating rate of 10 K min⁻¹ up to 600 °C. In this heating process, O₂ was released from the OCM in the mini honeycomb fill and led to the catalytic oxidation/partial oxidation of naphthalene. The intensities of the gas species after this catalytic oxidation process were then examined by MBMS at the exit of the furnace and the conversion ratio of naphthalene by each combined system can be identified. Finally, the mini honeycombs were cooled down to 300 °C and regenerated with air. Catalyst activity was tested in a similar experimental procedure as described above, only with oxygen provided by the inflow gas (He + naphthalene + O₂) instead of the OCMs.

The H₂S adsorption test was also carried out under the same experimental conditions. The CuO sorbent to be tested was placed upstream of the catalyst fill. The two fills were separated by an Al₂O₃ frit. During the test, the naphthalene

Table 2 – Composition of the four combined catalyst and OCM systems.

Material systems	Mass of catalyst [g kg ⁻¹]	Mass of OCM [g kg ⁻¹]
NiOC7	NiO – 70.5	CSFM – 929.5
NiOC4	NiO – 47.7	CSFM – 952.3
NiOC3	NiO – 37.2	CSFM – 962.8
NiOI7	NiO – 76.1	Ilmenite – 923.9

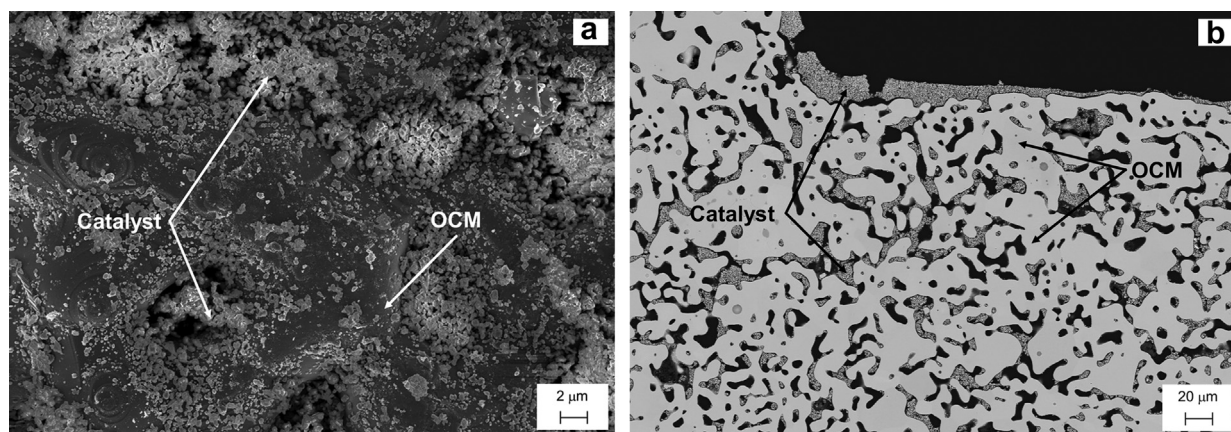


Fig. 2 – Scanning electron microscope pictures of the catalyst-coated OCM NiOC7: (a) surface; (b) cross section.

loaded carrier gas was first mixed with $140 \text{ cm}^3 \text{ m}^{-3} \text{ H}_2\text{S}$ at the gas inlet, then the gas mixture was led sequentially through both fills, where an adsorption of H_2S by the CuO sorbent and a conversion of naphthalene by the catalyst fill took place simultaneously. Before every experiment, the CuO sorbent was regenerated by air.

3. Results and discussion

3.1. Redox properties of the OCMs

The experimental results of the cyclic thermogravimetric measurements of the OCM (CSFM and ilmenite) are presented in Fig. 4. The weight change of the OCMs (absorption and release of O_2) was influenced by temperature and atmosphere, as can be seen in Fig. 4. Different temperature profiles during the oxygen release cycles (2nd and 4th cycles) were applied to both OCMs. The weight change of the OCMs indicates the release and absorption of O_2 . The oxygen release capacity of CSFM exhibited no significant increase at temperatures higher than $600 \text{ }^\circ\text{C}$, while that of ilmenite shows increased oxygen storage capacity with increasing temperature. After the cyclic test, the main phase of CSFM converted into a tetragonal Ruddlesden-Popper phase $\text{Sr}_3\text{Fe}_2\text{O}_7$, while the main phases of ilmenite showed no obvious changes.

The starting temperature, above which the oxygen-release first occurs, is listed together with the released or regenerated

portion of oxygen in different cycles of the two OCMs in Table 3. For CSFM, oxygen was released in the second and the fourth cycle above an almost identical temperature of about $301 \text{ }^\circ\text{C}$. The starting temperature of oxygen-release for ilmenite is about $327 \text{ }^\circ\text{C}$. By comparing the amount of oxygen being released and regenerated in different cycles, it can be seen that both materials showed excellent reversibility. In comparison with CSFM, ilmenite has a higher oxygen storage capacity under the same experimental conditions.

3.2. Catalyst activity and H_2S -sorption experiments

The catalytic activity of the selected catalyst NiO was investigated by MBMS. Fig. 5 (curve a) shows the naphthalene conversion ratio as a function of temperature by using 20 g NiO. The curve indicates that the naphthalene conversion ratio increases with increasing temperature. At $400 \text{ }^\circ\text{C}$, a naphthalene conversion ratio of over 80% was achieved; at

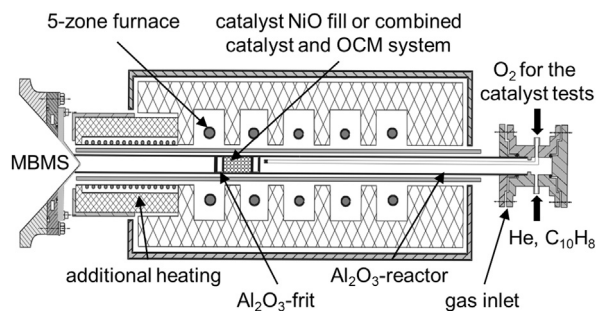


Fig. 3 – Experimental set up for catalyst tests and the combined catalyst and OCM system tests.

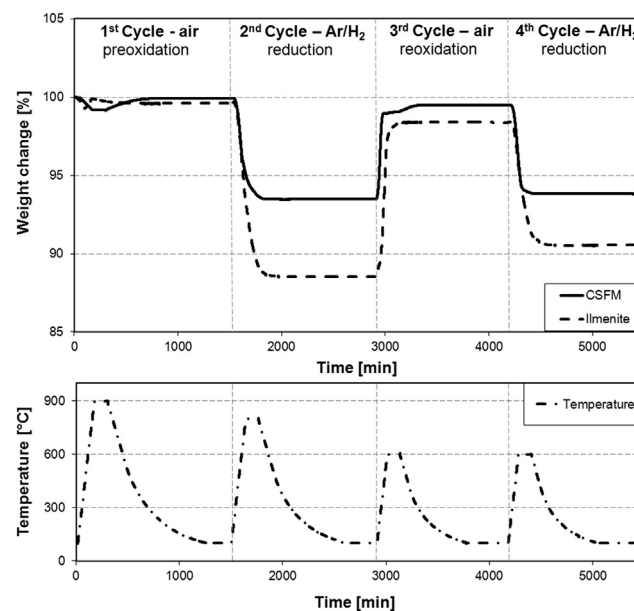


Fig. 4 – Weight change of the OCMs and temperature profile during the cyclic thermogravimetric measurements.

Table 3 – Released or regenerated oxygen portion in the last three cycles and starting temperature of oxygen-release in the oxygen release cycles.

Item	CSFM	Ilmenite
Released oxygen in 2nd cycle [L kg ⁻¹]	45.05	77.7
Regenerated oxygen in 3rd cycle [L kg ⁻¹]	42.01	69.05
Released oxygen in 4th cycle [L kg ⁻¹]	39.72	55.02
T of oxygen-release in 2nd cycle [°C]	300.6	326.5
T of oxygen-release in 4th cycle [°C]	301	327

600 °C, about 95% naphthalene was removed; at a temperature higher than 700 °C naphthalene was completely removed and converted to synthesis gas. With the help of XRD analysis, it was verified that the catalyst NiO remains as monophase after the measurements. The excellent naphthalene conversion ratio of NiO demonstrates its suitability as catalyst for the combined catalyst and oxygen carrier system.

To determine the influence of H₂S on the catalytic activity of NiO and the H₂S removal efficiency of CuO sorbent, 20 g catalyst fill with an additional CuO sorbent fill was tested under the mixed gas flow (He + 140 cm³ m⁻³ H₂S + naphthalene + O₂). In Fig. 5, the naphthalene conversion ratios under different experimental conditions are shown as a function of temperature. The curve b shows the influence of H₂S on the conversion ratio of naphthalene catalysed by NiO. Compared to the conversion ratio in non-contaminated gas (curve a), the conversion ratio under H₂S containing gas flow was lowered by 6.9% points at 600 °C. In particular, the conversion ratio at 400 °C was lowered by 27.8% points under H₂S containing gas flow. As expected, the trace gas H₂S caused a deactivation of NiO and thus led to a very low naphthalene conversion ratio.

The curve c in Fig. 5 represents the naphthalene conversion ratio for NiO together with a CuO sorbent under the mixed gas flow (He + 140 cm³ m⁻³ H₂S + naphthalene + O₂). Obviously, the CuO sorbent cannot only absorb the trace gas

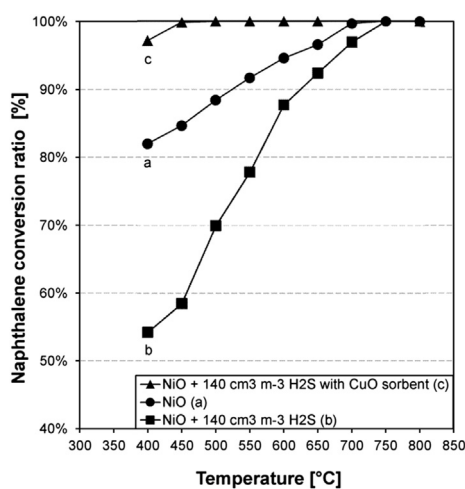


Fig. 5 – Conversion ratios of naphthalene with temperature catalysed by NiO under different testing conditions.

H₂S, but also partly catalyse the oxidation of naphthalene [20,21,28].

3.3. Naphthalene removal by the combined catalyst and OCM

After being separately investigated in the preliminary experiments, the selected catalyst and OCMs were then investigated in the next step as a combined system. 30 g of each of the four combined catalyst and OCM systems (Table 2) were manufactured and tested for their partial oxidation properties of naphthalene using MBMS. During the experiment, the carrier gas (He + 40 mmol mol⁻¹ H₂) together with naphthalene flew through the chosen system and were partially oxidized. The intensity changes of the product gas species (¹⁸H₂O⁺, ²⁹CO⁺, ³⁴O₂⁺, ⁴⁴CO₂⁺ and ¹²⁸C₁₀H₈⁺) with time/temperature are shown in Fig. 6. Hydrogen was not included here, because it has a very small molecular mass and cannot be easily detected by MBMS.

For all four combined catalyst and OCM systems, the intensity of naphthalene reached its maximum value after 2 min from the beginning of the experiment. Then it decreased with increasing temperature, because oxygen stored in the OCMs (CSFM, ilmenite) was released due to heating and naphthalene was thereby catalytically oxidized. The starting temperature for oxygen-release of CSFM and ilmenite are 301 °C and 327 °C, respectively, as being ascertained in the thermogravimetric experiments in Section 3.1.

The intensity of oxygen remained constant from the beginning of the experiment, since all oxygen released from the OCM was directly consumed by naphthalene removal. In addition to the products of complete oxidation, such as CO₂ and H₂O, the content of CO also significantly increased during the experiments. This confirms that partial oxidation of naphthalene took place.

At the end of the experiment, the furnace temperature reached 600 °C and was held at 600 °C for 10 min. During the heating period, the intensity of naphthalene started to increase again after reaching the lowest point in the material systems NiOC7 and NiOC4 while the intensity of CO₂ decreased in accordance. NiOC3 shows the same behaviour later, during the dwell time. These phenomena indicate a depletion of O₂ in the OCMs of these three material systems. The reason for the postponed oxygen depletion of NiOC3 might be caused by its larger amount of OCM (larger amount of oxygen) in relation to the amount of catalyst than the other two material systems under the same weight condition. On the contrary, the intensity of naphthalene and CO₂ in the material system NiOI7 did not change during the dwell time because of a higher oxygen storage capacity of the OCM (ilmenite). After the dwell time, the material systems were cooled down to 300 °C regenerated by air and tested in further cycles.

The naphthalene conversion ratios of all four material systems at 600 °C are shown in Fig. 7. The above described cyclic experiments were performed 10 times for each material system to test their reversibility. The results showed that the average naphthalene conversion ratio of the 3 material systems (CSFM + NiO) is over 97%, while that of the material

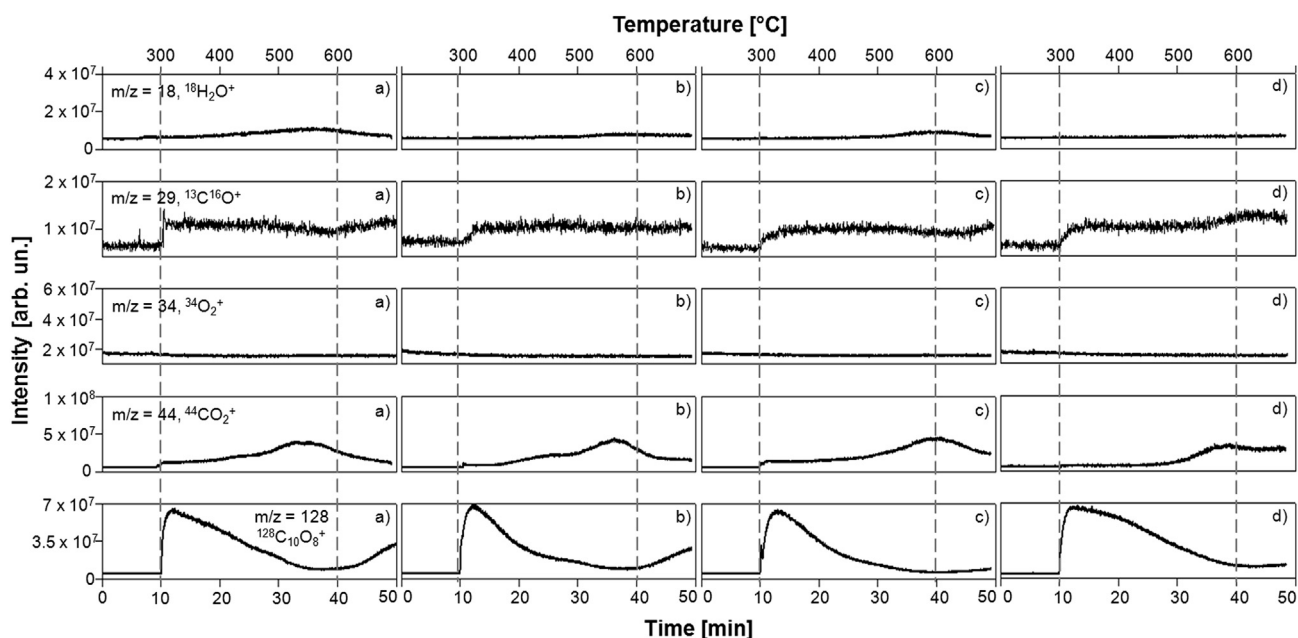


Fig. 6 – Intensity-Time-Profiles obtained during partial oxidation/oxidation of naphthalene at 300–600 °C in mixed gas (He + 40 mmol mol⁻¹ H₂ + naphthalene) with four different combined catalyst and OCM systems: (a) NiOC7; (b) NiOC4; (c) NiOC3; (d) NiOI7.

system (ilmenite + NiO) is over 95%. Especially NiOC3 has a naphthalene conversion ratio of more than 99%. The measurement deviation of all experiments is considered to be below 2%.

After the measurements, all four material systems were characterized by XRD. As a result, it was found that the main phases of all four material systems did not change after the

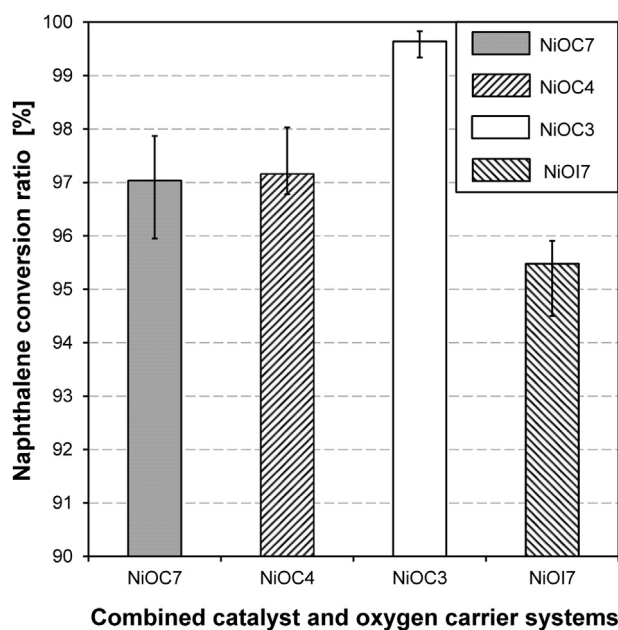


Fig. 7 – Conversion ratio of naphthalene at 600 °C with four different combined catalyst and OCM systems.

experiments. Nevertheless, Ni was found in all material systems after the experiments beside NiO.

4. Conclusions

In order to remove the tar formed during the biomass gasification process, a combined catalyst and OCM system was developed and several combinations of materials were investigated. The results of the four-cycle thermogravimetric measurements showed that both OCMs (CSFM and ilmenite) have very good oxygen storage capacities and reversible redox properties. It was also proved that the catalyst NiO has an excellent conversion ability of the tar model compound naphthalene.

The oxygen storage capacity as well as starting temperature for oxygen-release of the two OCMs (CSFM and ilmenite) and the catalytic activity of the catalyst (NiO) fit very well to the requirements of the partial oxidation of naphthalene. The use of the perovskite CSFM seems to be more meaningful for lower gas temperatures because of its lower temperature for oxygen generation, but ilmenite tolerates longer reduction time according to its higher oxygen storage capacity.

Results of the cyclic measurements showed that all four systems have very high naphthalene conversion ratios at 600 °C as well as very good reversibility and stability. Partial oxidation/oxidation of the naphthalene happened, which is proved by the observed increased intensities of CO and CO₂ measured by MBMS. CuO sorbent for trace gas (H₂S) elimination showed very good adsorption ability of H₂S and in addition a further catalytic effect for the naphthalene conversion process.

The results of this paper show that the developed combined catalyst and OCM systems are very efficient and reliable for naphthalene removal under laboratory conditions.

In future work, the materials discussed in this paper will be further tested in practical working systems. Thus, the influence of several contaminants in real raw producer gas, e.g. different tar compounds, sour gases, alkalis, and ash particles, will be investigated.

Acknowledgement

The work described in this paper has been done in the framework of the project “Catalytic Cleaning of Tar-containing Fuel Gases” financially supported by the Deutsche Bundesstiftung Umwelt (DBU) under the funding code AZ 27087.

REFERENCES

- [1] Gil J, Aznar MP, Caballero MA, Francés E, Corella J. Biomass gasification in fluidized bed at pilot scale with steam-oxygen mixtures. Product distribution for very different operating conditions. *Energy Fuels* 1997;11(6):1109–18.
- [2] Gil J, Corella J, Aznar MP, Caballero MA. Biomass gasification in atmospheric and bubbling fluidized bed: effect of the type of gasifying agent on the product distribution. *Biomass Bioenerg* 1999;17:389–403.
- [3] Devi L, Ptasiński KJ, Janssen FJJG. A review of the primary measures for tar elimination in biomass gasification processes. *Biomass Bioenerg* 2003;24:125–40.
- [4] Anis S, Zainal ZA. Tar reduction in biomass producer gas via mechanical, catalytic and thermal methods: a review. *Renew Sustain Energy Rev* 2011;15:2355–77.
- [5] Miyazawa T, Kimura T, Nishikawa J, Kunimori K, Tomishige K. Catalytic properties of Rh/CeO₂/SiO₂ for synthesis gas production from biomass by catalytic partial oxidation of tar. *Sci Technol Adv Mat* 2005;6:604–14.
- [6] Miyazawa T, Kimura T, Nishikawa J, Kado S, Kunimori K, Tomishige K. Catalytic performance of supported Ni catalysts in partial oxidation and steam reforming of tar derived from the pyrolysis of wood biomass. *Catal Today* 2006;115:254–62.
- [7] Lin YS, Maclean, Zeng YX. The Boc Group, Inc., Elevated temperature adsorption process. European patent EP 0913184B1. 1997 Oct 30.
- [8] Ullmann H, Guth U, Vashook VV, Burckhardt W, Götz RM, Bülow M. Oxid-keramiken mit hohem Sauerstofftransport. *Keram Z* 2005;57:72–8.
- [9] Ishida M, Jin H. Tokyo Electric Power Co., Inc., Chemical looping combustion power generation plant system. United States patent US 5447024. 1994 Sep 5.
- [10] Hossain MM, de Lasa HI. Chemical looping combustion (CLC) for inherent CO₂ separations - a review. *Chem Eng Sci* 2008;63:4433–51.
- [11] Böhning D. Katalytisch partielle oxidation polyzyklischer aromatischer Kohlenwasserstoff in Brenngasen aus der Biomassevergasung – modellierung und experimentelle Untersuchungen. Dissertation TU Dresden 2010.
- [12] Töpfer J, Pippardt U, Voigt I, Kriegel R. Structure, nonstoichiometry and magnetic properties of the perovskites Sr_{1-x}Ca_xMnO_{3-δ}. *Solid State Sci* 2004;6:647–54.
- [13] Kriegel R, Müller F, Reuner W, Sommer E. Patentanwälte Liedtke & Partner, assignee. Material zur reversiblen Sauerstoff-Speicherung sowie dessen Verwendung. Germany patent DE 102005034071A1. 2005 July 21.
- [14] Han KR, Jeong Y, Lee H, Kim CS. Fabrication of NiO/YSZ anode material for SOFC via mixed NiO precursors. *Mater Lett* 2007;61:1242–5.
- [15] Droushiotis N, Doraswami U, Kanawka K, Kelsall GH, Li K. Characterization of NiO-yttria stabilised zirconia (YSZ) hollow fibres for use as SOFC anodes. *Solid State Ionics* 2009;180:1091–9.
- [16] Coll R, Salvadó J, Farriol X, Montané D. Steam reforming model compounds of biomass gasification tars: conversion at different operating conditions and tendency towards coke formation. *Fuel Process Technol* 2001;74:19–31.
- [17] Bangala DN, Abatzoglou N, Chornet E. Steam reforming of naphthalene on Ni-Cr/Al₂O₃ catalysts doped with MgO, TiO₂, and La₂O₃. *AIChE J* 1998;44:927–36.
- [18] Furusawaa T, Tsutsumi A. Development of cobalt catalysts for the steam reforming of naphthalene as a model compound of tar derived from biomass gasification. *Appl Catal A-Gen* 2005;278:195–205.
- [19] Wang TJ, Chang J, Wu CZ, Fu Y, Chen Y. The steam reforming of naphthalene over a nickel-dolomite cracking catalyst. *Biomass Bioenerg* 2005;28:508–14.
- [20] Ferrandon M, Carnö J, Järas S, Björnbohm E. Total oxidation catalysts based on manganese or copper oxides and platinum or palladium II: activity, hydrothermal stability and sulphur resistance. *Appl Catal A-Gen* 1999;180:153–61.
- [21] Noichi H, Uddin A, Sasaoka E. Steam reforming of naphthalene as model biomass tar over iron-aluminum and iron-zirconium oxide catalyst catalysts. *Fuel Process Technol* 2010;91:1609–16.
- [22] Albertazzi S, Basile F, Brandin J, Einvall J, Fornasari G, Hultberg C, et al. Effect of fly ash and H₂S on a Ni-based catalyst for the upgrading of a biomass-generated gas. *Biomass Bioenerg* 2008;32:345–53.
- [23] Stemmler M, Müller M. Chemical hot gas cleaning concept for the “CHRISGAS” process. *Biomass Bioenerg* 2011;35:105–15.
- [24] Stemmler M, Tamburro A, Mueller M. Laboratory investigations on chemical hot gas cleaning of inorganic trace elements for the “UNIQUE” process. *Fuel* 2011. <http://dx.doi.org/10.1016/j.fuel.2011.05.027>.
- [25] Loesch HW, Kleinrahm R, Wagner W. Neue Magnetschwebewaagen für gravimetrische Messungen in der Verfahrenstechnik. *Chem Ing Techn* 1994;66:1055–8.
- [26] Dayton DC, French RJ, Milne TA. Direct observation of alkali vapor release during biomass combustion and gasification, 1. Application of molecular-beam mass-spectrometry to switchgrass combustion. *Energ Fuel* 1995;9:855–65.
- [27] Dayton DC, Frederick WWJ. Direct observation of alkali vapor release during biomass combustion and gasification, 2. Black liquor combustion at 1100 °C. *Energ Fuel* 1996;10:284–92.
- [28] Ferrandon M, Carnö J, Järas S, Björnbohm E. Total oxidation catalysts based on manganese or copper oxides and platinum or palladium I: characterisation. *Appl Catal A-Gen* 1999;180:141–51.